



Vibrational properties of MnO and NiO from DFT + U -based density functional perturbation theory

A. Floris,^{1,2} S. de Gironcoli,³ E. K. U. Gross,^{2,4} and M. Cococcioni⁵

¹*Department of Physics, King's College London, London, Strand WC2R 2LS, United Kingdom*

²*European Theoretical Spectroscopy Facility (ETSF)*

³*SISSA Condensed Matter Theory sector and CNR-IOM DEMOCRITOS Simulation Centre, via Bonomea 265, I-34136 Trieste, Italy*

⁴*Max-Planck-Institut für Mikrostrukturphysik, Weinberg 2, D-06120 Halle, Germany*

⁵*Department of Chemical Engineering and Materials Science, University of Minnesota, 421 Washington Avenue SE, Minneapolis, Minnesota 55455, USA*

(Received 27 September 2011; published 13 October 2011)

We introduce an extension of the density functional perturbation theory (DFPT) that allows self-consistent linear-response calculations from a DFT + U ground state. Using this scheme, the full phonon dispersion of strongly correlated materials, whose ground state can be captured with Hubbard-corrected functionals, can be accessed with unprecedented accuracy and numerical efficiency. The tool is applied to the study of MnO and NiO in their antiferromagnetic (AFII) ground state. Our results confirm the highly noncubic behavior of these systems and show a strong interplay between features of the phonon spectrum and the occupation of specific d states, suggesting the possibility to investigate the electronic structure of these materials through the analysis of their phonon spectrum.

DOI: 10.1103/PhysRevB.84.161102

PACS number(s): 71.27.+a, 63.20.D-

Late transition-metal (TM) monoxides (MnO, FeO, CoO, NiO), the prototypes of strongly correlated systems, are well known to be poorly described by density functional theory (DFT) within the commonly used approximate functionals, such as local density approximation (LDA) and generalized gradient approximation (GGA). Their insulating antiferromagnetic (AFII) state, however, can be captured quite accurately by the popular DFT + U (Ref. 1) scheme,²⁻⁵ based on a Hubbard-model additive correction to the DFT Hamiltonian.⁶⁻¹¹ In this Rapid Communication we exploit the DFT + U improved description of the electronic ground state of these systems to accurately compute their vibrational properties.

In the past decades the lattice vibrations of TM monoxides have been investigated quite intensively with experimental techniques.¹²⁻¹⁶ Calculations, however, have been more sparse¹⁷⁻²² and, with the exception of Ref. 18 [a Green-function-based method from a DFT + dynamical mean field theory (DMFT) functional], none of them was based on linear response theory, which is computationally much more efficient than methods requiring a supercell (e.g., “frozen phonon”).

In this Rapid Communication we extend the formulation of density functional perturbation theory (DFPT)²³ to the DFT + U Hamiltonian. This allows calculations of the entire vibrational spectrum of the DFT + U ground state of correlated materials with unprecedented accuracy and efficiency. Moreover, by computing the Hubbard U through the linear-response method of Ref. 24, our scheme is completely parameter free. “DFPT + U ” numerical results will be shown for MnO and NiO in their antiferromagnetic (low-temperature) phase. The two GGA + U vibrational spectra will be analyzed in detail and compared with GGA results and with available experimental data.

DFPT is based on the application of first-order perturbation theory to the ground state of the self-consistent Kohn-Sham (KS) Hamiltonian (see Ref. 23, Sec. II C, whose notation is adopted in the following). The displacement of an ion L in direction α from its equilibrium position induces a perturbation $\Delta^\lambda V_{\text{SCF}}$ in the electronic KS potential V_{SCF} , leading to a

variation $\Delta^\lambda n(r)$ of the charge density ($\lambda \equiv \{L\alpha\}$). Since the Hubbard potential V_{Hub} is a corrective addition to the KS potential, its variation $\Delta^\lambda V_{\text{Hub}}$ must be added to $\Delta^\lambda V_{\text{SCF}}$ when solving the DFPT equations.²³ The V_{Hub} expression reads⁵

$$V_{\text{Hub}} = \sum_{I\sigma mm'} U^I \left[\frac{\delta_{mm'}}{2} - n_{mm'}^{I\sigma} \right] |\varphi_m^I\rangle \langle \varphi_m^I|. \quad (1)$$

In Eq. (1), the atomic occupations $n_{mm'}^{I\sigma}$ are computed projecting the KS states $|\psi_i^\sigma\rangle$ on atomic orbitals $|\varphi_m^I\rangle$, i.e., $n_{mm'}^{I\sigma} = \sum_i^{\text{occ}} \langle \psi_i^\sigma | \varphi_m^I \rangle \langle \varphi_m^I | \psi_i^\sigma \rangle$; I and m represent indexes of the atomic site and state, respectively.²⁴ The linear response of the Hubbard potential then reads

$$\begin{aligned} \Delta^\lambda V_{\text{Hub}} = & \sum_{I\sigma mm'} U^I \left[\frac{\delta_{mm'}}{2} - n_{mm'}^{I\sigma} \right] [|\Delta^\lambda \varphi_m^I\rangle \langle \varphi_m^I| \\ & + |\varphi_m^I\rangle \langle \Delta^\lambda \varphi_m^I|] - \sum_{I\sigma mm'} U^I \Delta^\lambda n_{mm'}^{I\sigma} |\varphi_m^I\rangle \langle \varphi_m^I|, \end{aligned} \quad (2)$$

where $\Delta^\lambda \varphi_m^I$ is the response of the atomic wave function φ_m^I due to a shift in the position of its center and

$$\begin{aligned} \Delta^\lambda n_{mm'}^{I\sigma} = & \sum_i^{\text{occ}} \{ \langle \psi_i^\sigma | \Delta^\lambda \varphi_m^I \rangle \langle \varphi_m^I | \psi_i^\sigma \rangle + \langle \psi_i^\sigma | \varphi_m^I \rangle \langle \Delta^\lambda \varphi_m^I | \psi_i^\sigma \rangle \} \\ & + \sum_i^{\text{occ}} \{ \langle \Delta^\lambda \psi_i^\sigma | \varphi_m^I \rangle \langle \varphi_m^I | \psi_i^\sigma \rangle + \langle \psi_i^\sigma | \varphi_m^I \rangle \langle \varphi_m^I | \Delta^\lambda \psi_i^\sigma \rangle \}. \end{aligned} \quad (3)$$

Note that, in Eq. (2), the terms arising from the variation $\Delta^\lambda U^I$ are assumed to be negligible. In Eq. (3), $|\Delta^\lambda \psi_i^\sigma\rangle$ is the KS state linear response to the atomic displacement, computed solving the DFPT equations (Ref. 23, Sec. II C).

Once the density response $\Delta^\lambda n(r) = 2 \text{Re} \sum_{i\sigma}^{\text{occ}} \psi_i^{*\sigma} \Delta^\lambda \psi_i^\sigma$ is obtained, the dynamical matrix can be constructed and the phonon frequencies and vibrational modes are

calculated. However, the Hubbard energy correction $E_{\text{Hub}} = \frac{1}{2} \sum_{l\sigma mm'} U^I (\delta_{mm'} - n_{mm'}^{l\sigma}) n_{mm'}^{l\sigma}$ will contribute to the standard (LDA/GGA) dynamical matrix with the following additional term:

$$\Delta^\mu (\partial^\lambda E_{\text{Hub}}) = \sum_{l\sigma mm'} U^I \left[\frac{\delta_{mm'}}{2} - n_{mm'}^{l\sigma} \right] \Delta^\mu (\partial^\lambda n_{mm'}^{l\sigma}) - \sum_{l\sigma mm'} U^I \Delta^\mu n_{mm'}^{l\sigma} \partial^\lambda n_{mm'}^{l\sigma}, \quad (4)$$

namely, the total derivative of the Hubbard contribution $\partial^\lambda E_{\text{Hub}}$ to Hellmann-Feynman forces.²⁵ In Eq. (4), ∂^λ indicates a *bare* derivative, i.e., taken at fixed orbitals ψ_i^σ .²⁶ Finally, in the case of insulators and semiconductors, a “nonanalytical” term $C_{l\alpha, j\beta}^{na}$ must be added to the dynamical matrix to account for the coupling of longitudinal vibrations with the macroscopic electric field generated by ionic displacements. This term, responsible for the LO-TO splitting at $\mathbf{q} = \Gamma$, depends on the Born effective-charge tensor \mathbf{Z}^* and the high-frequency electronic dielectric tensor ϵ^∞ : $C_{l\alpha, j\beta}^{na} = \frac{4\pi e^2}{\Omega} \frac{(\mathbf{q} \cdot \mathbf{Z}_l^*)_\alpha (\mathbf{q} \cdot \mathbf{Z}_j^*)_\beta}{\mathbf{q} \cdot \epsilon^\infty \cdot \mathbf{q}}$.²⁷ The calculation of $\mathbf{Z}_{l, \alpha\beta}^*$ and $\epsilon_{\alpha\beta}^\infty$ is based on the response of the electronic system to a macroscopic electric field and requires the evaluation of the transition amplitudes between valence and conduction KS states promoted by the commutator of the KS Hamiltonian with the position operator \mathbf{r} , $\langle \psi_{c, \mathbf{k}} | [H_{\text{SCF}}, \mathbf{r}] | \psi_{v, \mathbf{k}} \rangle$.²⁸ A finite contribution to this quantity comes from the presence of the (nonlocal) Hubbard potential

$$\begin{aligned} & \langle \psi_{c, \mathbf{k}}^\sigma | [V_{\text{Hub}}^\sigma, r_\alpha] | \psi_{v, \mathbf{k}}^\sigma \rangle \\ &= \sum_{lmm'} U^I \left[\frac{\delta_{mm'}}{2} - n_{mm'}^{l\sigma} \right] \\ & \times \left[-i \langle \psi_{c, \mathbf{k}}^\sigma | \frac{d}{dk_\alpha} (|\varphi_{m, \mathbf{k}}^l\rangle \langle \varphi_{m', \mathbf{k}}^l|) | \psi_{v, \mathbf{k}} \rangle \right], \quad (5) \end{aligned}$$

where $\varphi_{m, \mathbf{k}}^l$ are Bloch sums of atomic wave functions and k_α is a component of the Bloch vector \mathbf{k} .

To summarize, the extension of DFPT to the DFT + U functional amounts to the definition and implementation of *three* contributions: (i) the variation of the Hubbard potential $\Delta^\lambda V_{\text{Hub}}$ to be added to $\Delta^\lambda V_{\text{SCF}}$; (ii) the second derivative $\Delta^\mu (\partial^\lambda E_{\text{Hub}})$ to be added to the analytical part of the dynamical matrix; and (iii) a term to the “nonanalytical” dynamical matrix.

This DFPT extension was implemented in the PHONON code of the QUANTUM ESPRESSO package.²⁹ Although the formalism presented above is valid only for norm-conserving (NC) pseudopotentials and for insulators, our implementation has been extended to ultrasoft (US) pseudopotentials^{26,30} and metallic systems. The corresponding formal extension, crucial for efficient calculations of systems with localized electrons, will be presented in a future publication.

We now discuss the phonon spectrum of MnO and NiO, obtained with this approach.³¹ The U^I values were determined via the linear-response approach of Ref. 24, leading to $U^{\text{Mn}} = 5.25$ eV and $U^{\text{Ni}} = 5.77$ eV.

MnO and NiO crystallize in the cubic rock-salt structure but acquire a rhombohedral symmetry due to their antiferromagnetic order consisting of ferromagnetic (111) planes of cations alternating with opposite magnetization. DFT + U has been used quite successfully to characterize this AFII ground state.^{6,10}

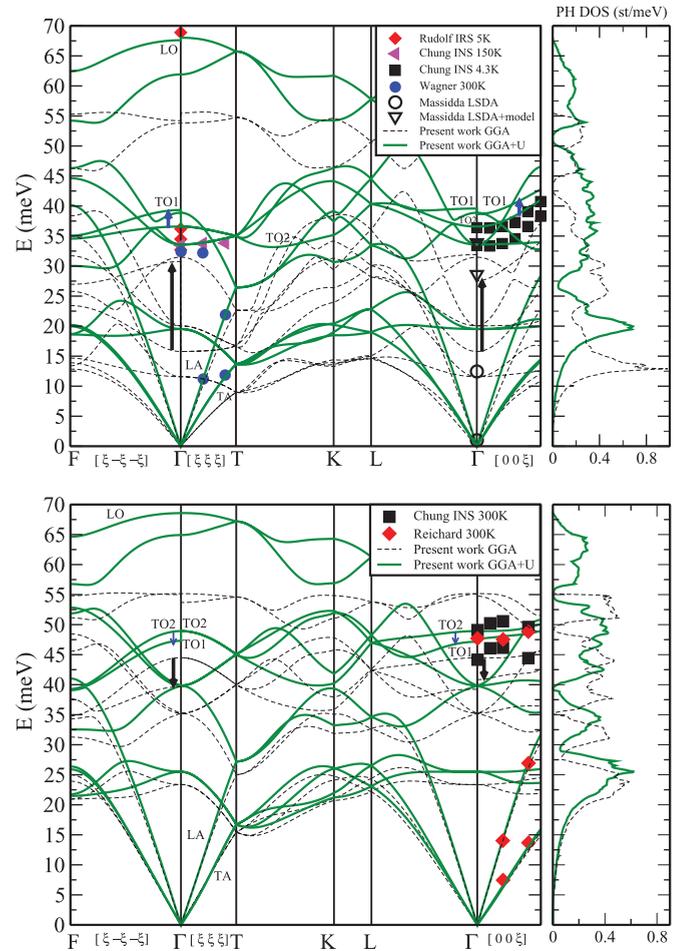


FIG. 1. (Color online) MnO (upper panel) and NiO (lower) phonon dispersion, calculated in GGA (dashed lines) and GGA + U (solid thick lines). Blue (black) arrows mark the GGA + U (GGA) magnetic splittings and their sign (see text). Upper panel: Filled symbols represent experimental data (Refs. 12,13 and 15), and open symbols the results of other calculations (at zone center) (Ref. 17). Lower panel: Symbols represent experimental data (Refs. 12 and 16). Note that for NiO the arrows point downward to indicate the sign difference with respect to MnO. Right-hand panels: Phonon DOS.

Figure 1 (upper panel) shows the MnO phonon dispersion calculated with GGA and GGA + U . The most evident effect brought about by the Hubbard correction is a general upward shift of the frequencies, making the GGA + U spectrum in much better agreement than GGA with available experiments,^{12,13,15} for both acoustic and optical branches (also confirming the accuracy of the linear-response calculation²⁴ of the Hubbard parameter). Note in particular the considerable improvement over GGA in the calculation of LO and TO frequencies at $\mathbf{q} = \Gamma$ (GGA underestimates the LO frequency by ≈ 15 meV). The frequency shift is clearly illustrated in the phonon density of states (DOS) (Fig. 1, right-hand panel), exhibiting also a different weight distribution, with a more disperse structure in the GGA + U case. A second noteworthy change consists in a substantial reduction of the splitting between the TO modes in the $[1\bar{1}\bar{1}]$ and $[001]$ directions. Along these directions, the discontinuous and continuous modes at the zone center are indicated as TO1 and TO2 and correspond

to counterphase vibrations of the Mn and O sublattices. Both transverse optical modes along [111] are polarized in the (111) ferromagnetic planes. Along $[1\bar{1}\bar{1}]$ and [001] directions, the transverse mode TO2 also vibrates parallel to the (111) planes and is continuous at $\mathbf{q} = \Gamma$. Transverse mode TO1, instead, vibrates out of these planes for $\mathbf{q} \in [1\bar{1}\bar{1}]$ and $\mathbf{q} \in [001]$ (along [211] and [110], respectively) and the inequivalence between {111} planes due to magnetism causes the TO1 to be discontinuous and to split from TO2. A similar effect, although less pronounced, can also be observed for LO modes. These splittings are absent in the paramagnetic cubic phase.²⁰ In fact, as pointed out by Massidda *et al.*,¹⁷ the TO splitting has a purely magnetic origin.

The splitting reduction was interpreted in Ref. 17 as a consequence of the suppression of the Mn-O hybridization, produced by the stronger localization of d states due to the Hubbard correction. The latter also results in a concomitant increase of the KS electronic band gap. An alternative, albeit equivalent, way to understand the magnetic splitting reduction is through the superexchange mechanism, expected to be responsible for the magnetic coupling J between metal ions.^{33–36} In fact, according to second-order perturbation theory, $J \propto t^2/\Delta$, where t is the hopping amplitude between d and p states and Δ is their energy separation. A larger U destabilizes empty (minority-spin) d states, resulting in a substantial increase of Δ and a reduction of J .

The phonon dispersion of NiO is presented in Fig. 1 (lower panel). Overall, NiO shows the same trends observed in MnO: The Hubbard correction shifts the frequencies upward (in a less pronounced way than in MnO), improving the agreement with experiments.^{12,37} Also for NiO the magnetic splitting Δ_{TO} significantly contracts in comparison to GGA. At variance with MnO, however, TO1 splits *downward* along the [001] and the $[1\bar{1}\bar{1}]$ directions, appearing softer than TO2. In Ref. 19 the splitting Δ_{TO} (and, in particular, its sign) has been related to the magnetic coupling between metal ions according to the formula $\Delta_{\text{TO}} = \frac{d^2 J_1}{dQ_x dQ_y}$, where Q_x and Q_y are atomic displacements along two directions parallel to the side of the cubic cell. Thus, a change in the sign of the nearest-neighbor magnetic coupling J_1 , as found in Ref. 19, could be responsible for the inverted order of TO1 and TO2. While this is consistent with the experimental results from Ref. 37, it seems in contrast with the ones of Chung *et al.*¹² (believed to be “more controversial”¹⁹), who do not observe a sign change in the splittings of NiO and MnO. Our results confirm those of Ref. 19. We notice, moreover, that the sign of Δ_{TO} correlates with the occupation of specific subsets of orbitals, namely, the minority-spin e_g states. At ambient pressure, the metal ions of all late TM monoxides have maximum magnetization, with five electrons in the majority-spin d orbitals and the rest in the minority-spin counterparts. From MnO to NiO the number of minority-spin d electrons varies from 0 to 3 (FeO has 1, CoO has 2). The d states of TM ions in octahedral coordination with O, as in these compounds, are subjected to a crystal field that splits them into a doublet (e_g) and a triplet (t_{2g}), with the latter at lower energy. e_g states point along the TM-O directions, while the t_{2g} are directed toward the midpoint of the sides of the oxygen octahedra. The AFII-induced rhombohedral symmetry further splits the t_{2g}

triplet in a second doublet (e'_g) with e_g symmetry and a lone state a_{1g} that corresponds to a z^2 state along the [111] cubic diagonal. In MnO the minority-spin states, nominally empty, show a residual occupation (due to the incomplete transfer of electrons from the Mn to the O) that mostly concentrates on the e_g states. NiO, instead, has nominally three minority-spin electrons, mostly concentrated on t_{2g} (e'_g and a_{1g}) states, with higher-energy e_g states almost empty. Going from MnO to NiO, as the occupation of the minority-spin states increases, t_{2g} orbitals become more and more stable and their occupation eventually becomes larger than that of e_g states. We argue that the Δ_{TO} change of sign is related to this crossover. In fact, when minority-spin e_g states are more occupied, more electronic charge is concentrated in the TM-O “bonds,” making them stronger and increasing the frequency of the TO1 mode. When t_{2g} states are occupied, instead, the electronic charge points toward interstitial spaces and the energy required by the TO1 vibration of the two sublattices against each other along directions oblique to the (111) planes is lower than that of vibrations parallel to these planes (TO2) that bring t_{2g} states to partially overlap with oxygen p orbitals. While not strictly quantitative, this scenario seems consistent with what was observed in some Fe compounds under pressure, where the transition from a high-spin state to a low-spin one (with the conversion of the majority e_g electrons into minority t_{2g} manifold) is accompanied by a significant softening of the bulk modulus.³⁸ Further calculations (not presented here) on CoO (two minority-spin electrons) and CoO^+ (one minority-spin electron) confirm this interpretation: While CoO (with low-lying occupied e'_g , and essentially unoccupied e_g) behaves as NiO, CoO^+ (with a_{1g} occupied and e_g partially occupied) has a splitting of the same sign as MnO. The occupation of the minority e_g states can also be related to the change in the sign of J_1 through superexchange theory.^{33–36} Lower occupations of these orbitals increase the weight of virtual transitions to them and make the interactions more strongly negative (ferromagnetic). In this view, the change of sign of J_1 and of the magnetic splitting can be regarded as consequences of the redistribution of electrons on the TM d states. A detailed study of the vibrational properties of strongly correlated materials can therefore shed light on their electronic structure and magnetic interactions.

To summarize: In this Rapid Communication we have introduced an extension of DFPT allowing linear response calculations from a DFT + U ground state. The scheme represents a highly efficient method to calculate the entire vibrational spectrum of systems with strong electronic correlation. The approach exploits two computational advantages of DFPT and DFT + U : (i) the possibility to avoid supercell calculations and (ii) the affordable cost of the Hubbard correction in the calculations of the total energy and its derivatives. The excellent agreement with experimental measurements obtained for MnO and NiO demonstrates the accuracy of the computational tool. In addition, the results suggest the possibility to investigate fine details of the electronic structure of these materials through their signature on the vibrational spectrum. The methodological extension introduced here will be crucial to study the behavior of TM compounds at finite temperature and in studies requiring a

highly accurate vibrational spectrum, e.g., calculations of the electron-phonon coupling in high- T_c superconductors.

We thank Sandro Massidda for useful discussions. The authors are also grateful to the Minnesota Supercomputing

Institute for providing computational resources that were used for part of the calculations presented in this Rapid Communication. This work was supported by the Deutsche Forschungsgemeinschaft through SPP11 and by the NSF Grant No. EAR-0810272.

-
- ¹DFT + U will indicate LDA + U or GGA + U , according to the approximate DFT functional used.
- ²V. I. Anisimov, J. Zaanen, and O. K. Andersen, *Phys. Rev. B* **44**, 943 (1991).
- ³V. I. Anisimov, I. S. Elfimov, N. Hamada, and K. Terakura, *Phys. Rev. B* **54**, 4387 (1996).
- ⁴V. I. Anisimov, F. Aryasetiawan, and A. I. Lichtenstein, *J. Phys. Condens. Matter* **9**, 767 (1997).
- ⁵S. L. Dudarev, G. A. Botton, S. Y. Savrasov, C. J. Humphreys, and A. P. Sutton, *Phys. Rev. B* **57**, 1505 (1998).
- ⁶O. Bengone, M. Alouani, P. Blöchl, and J. Hugel, *Phys. Rev. B* **62**, 16392 (2000).
- ⁷T. Tsuchiya, R. M. Wentzcovitch, C. R. S. da Silva, and S. de Gironcoli, *Phys. Rev. Lett.* **96**, 198501 (2006).
- ⁸W.-B. Zhang, Y.-H. Deng, Y.-L. Hu, K.-L. Han, and B.-Y. Tang, *Solid State Commun.* **142**, 6 (2007).
- ⁹T. Cai, H. L. Han, Y. Yu, T. Gao, J. G. Du, and L. H. Hao, *Physica B* **404**, 89 (2009).
- ¹⁰V. L. Campo Jr. and M. Cococcioni, *J. Phys. Condens. Matter* **22**, 055602 (2010).
- ¹¹K. Karlsson, F. Aryasetiawan, and O. Jepsen, *Phys. Rev. B* **81**, 245113 (2010).
- ¹²E. M. L. Chung, D. M. Paul, G. Balakrishnan, M. R. Lees, A. Ivanov, and M. Yethiraj, *Phys. Rev. B* **68**, 140406 (2003).
- ¹³T. Rudolf, C. Kant, F. Mayr, and A. Loidl, *Phys. Rev. B* **77**, 024421 (2008).
- ¹⁴B. C. Haywood and M. F. Collins, *J. Phys. C* **4**, 1299 (1971).
- ¹⁵V. Wagner, W. Reichardt, and W. Kress, *Proc. Conf. Neutron Scattering* **1**, 175 (1976).
- ¹⁶W. Reichardt, V. Wagner, and W. Kress, *J. Phys. C* **8**, 3955 (1975).
- ¹⁷S. Massidda, M. Posternak, A. Baldereschi, and R. Resta, *Phys. Rev. Lett.* **82**, 430 (1999).
- ¹⁸S. Y. Savrasov and G. Kotliar, *Phys. Rev. Lett.* **90**, 056401 (2003).
- ¹⁹W. Luo, P. Zhang, and M. L. Cohen, *Solid State Commun.* **142**, 504 (2007).
- ²⁰U. D. Wdowik and D. Legut, *J. Phys. Condens. Matter* **21**, 275402 (2009).
- ²¹Y. Wang, J. E. Saal, J.-J. Wang, A. Saengdeejing, S.-L. Shang, L.-Q. Chen, and Z.-K. Liu, *Phys. Rev. B* **82**, 081104 (2010).
- ²²S. Y. Park and H. J. Choi, *Phys. Rev. B* **80**, 155122 (2009).
- ²³S. Baroni, S. de Gironcoli, A. Dal Corso, and P. Giannozzi, *Rev. Mod. Phys.* **73**, 515 (2001).
- ²⁴M. Cococcioni and S. de Gironcoli, *Phys. Rev. B* **71**, 35105 (2005).
- ²⁵M. Cococcioni, *Rev. Mineral. Geochem.* **71**, 147 (2010).
- ²⁶A. Dal Corso, *Phys. Rev. B* **64**, 235118 (2001).
- ²⁷W. Cochran and R. A. Cowley, *J. Phys. Chem. Solids* **23**, 447 (1962).
- ²⁸P. Giannozzi, S. de Gironcoli, P. Pavone, and S. Baroni, *Phys. Rev. B* **43**, 7231 (1991).
- ²⁹P. Giannozzi *et al.*, *J. Phys. Condens. Matter* **21**, 395502 (2009).
- ³⁰D. Vanderbilt, *Phys. Rev. B* **41**, 7892 (1990).
- ³¹Calculations were performed at the experimental constants for both materials, in their cubic undistorted structure. We used ultrasoft pseudopotentials with a GGA-PBE xc functional (Ref. 32). A wavefunction (charge) energy cutoff of 60 Ry (600 Ry) and a Monkhorst-Pack grid of $10^3 \mathbf{k}$ points for self-consistent field (SCF) and phonon calculations were sufficient to converge all the modes within 3%. Phonon dispersions were obtained interpolating from a $4 \times 4 \times 4$ grid of \mathbf{q} vectors.
- ³²J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
- ³³P. W. Anderson, *Phys. Rev.* **79**, 350 (1950).
- ³⁴J. B. Goodenough, *J. Phys. Chem. Solids* **6**, 287 (1958).
- ³⁵P. W. Anderson, *Phys. Rev.* **115**, 2 (1959).
- ³⁶J. Kanamori, *J. Phys. Chem. Solids* **10**, 87 (1959).
- ³⁷M. T. Hutchings and E. J. Samuelsen, *Phys. Rev. B* **6**, 3447 (1972).
- ³⁸H. Hsu, P. Blaha, M. Cococcioni, and R. M. Wentzcovitch, *Phys. Rev. Lett.* **106**, 118501 (2011).